



WEATHERING OF PE PIPES

By M Stahmer, Vinidex Pty Ltd
and Dr P Micic, Qenos Pty Ltd
November, 2003

When exposed outdoors to weathering the properties of polymers, such as human skin, timber and plastics, are subject to change. Primarily, the effect is one of photo-oxidation brought about by incident wavelengths within the ultraviolet range, although additional factors may contribute. In the case of plastics, photo-oxidation may result in loss of impact strength, resistance to slow crack growth, and thermal stability. This is a surface effect, and the bulk polymer is not necessarily affected. Pigment fade may also be a consideration.

This Technical Note addresses end-user performance requirements for short and long term exposure of PE pipes and the means of optimising compound performance. It is not intended to be a treatise on weathering of polymers, a subject already covered in detail in the literature.

The discussion relates to pipes manufactured in accordance with AS/NZS 4130:2003 - Polyethylene (PE) pipes for pressure applications, and AS/NZS 4131:2003 - Polyethylene (PE) compounds for pressure pipes and fittings.

End-user Requirements:

- i. Water (WSAA) and gas (AGA) industries require pipes to be suitable for use after two years of outdoors exposure during storage in Australia.
- ii. In the case of black pipes, WSAA allows permanent exposure for above ground PE sewers. Other industries, such as mining, require up to 15 years of exposure during service.

Means of protection:

Protective additives such as carbon black and hindered amine light stabilisers (HALS) are used in order to minimise degradation. The use of carbon black optimises UV stabilisation and thus black pipes dominate general usage.

For coloured compounds, stabilisation has not been as effective as carbon black, but the introduction of HALS (hindered amine light stabilisers) has enabled greatly improved UV resistance, albeit still not to the level of carbon black.

Requirements for additives and product performance are included in AS/NZS 4130 and AS/NZS 4131.

i. Carbon Black

Carbon black as specified in AS/NZS 4131 will confer excellent long term retention of properties, hence the predominant use of this additive for PE pipes. For stabilisation, the key attributes of the carbon black are particle size and distribution, plus volatile content as specified in AS/NZS 4131.

Although actual long term performance is not well documented quantitatively, there are sufficient data and long term history of use for black PE pipe grades to assume suitability.

Chevron Phillips Chemical Company LP ⁽¹⁾ have exposed black HDPE and MDPE pipe materials conforming with AS/NZS 4131, plus materials with non-conforming carbon black, for over nine years and seven years respectively in Singapore, where incident energy is about 80% of that in Nth. Queensland. These pipes, whilst exhibiting surface oxidation, showed undiminished hydrostatic pressure resistance, even for non-conforming carbon black (50 nm particle size) used for comparative purposes.

Gaz De France⁽²⁾ reported exposure of pipes for 38 months in the South of France (approx. equal to 24 months in Nth. Queensland) - these were black MDPE pipe grades. Oxidation occurred to a depth of approximately 50µm, which was described as the general order of magnitude for black MDPE gas pipes. Taking into account that surface layers are removed prior to fusion welding and there is a "universal" allowance of 10% of pipe wall for surface damage during handling and installation, the small amount of surface oxidation is negligible.

ii. HALS


The development of HALS stabilisers has resulted in significantly improved long term resistance to the effects of UV radiation on coloured compounds. Such compounds are used as pipe identification and may be used as coextrusions on pipes or for the pipes themselves.

The performance of HALS stabilisers is well documented and acknowledged within AS/NZS 4130 by acceptance of 0.2% of HALS as being adequate for exposure during storage in Australia.

According to Ciba Specialty Chemicals, addition of 0.2% HALS Tinuvin 783 provides life of more than 16000 hours, compared with less than 1000h with nil stabilisation, as measured by carbonyl absorbance of the sample exposed to weathering in Weather-Ometer.

Performance of a Combination of Polymeric HALS in PE-HD Plaques (2mm)

Sample: PE-HD-9 (Ti catalyst, d=0.960)
Base Stabilization: 0.03% Irganox 1076 + 0.1% Ca Stearate
Exposure: WOM Ci 65 , BPT ~63°C, dry
Test Criterion: Hours to 0.5 Carbonyl Absorbance

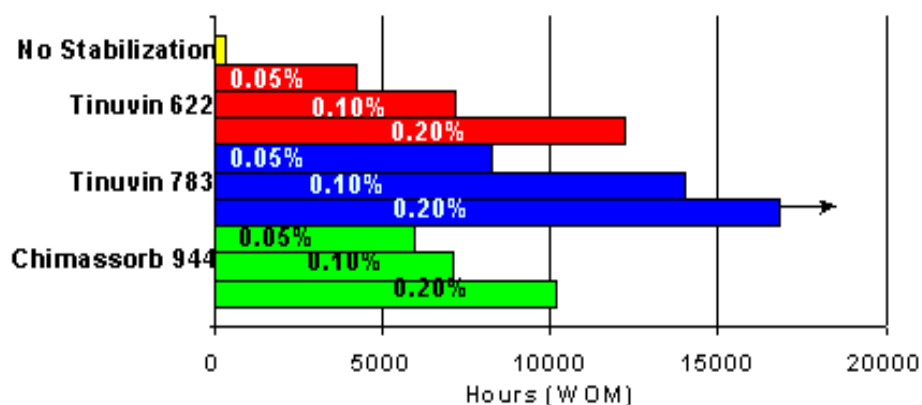

Based on Ciba Specialty Chemicals data, 16000 hours in the Weather-Ometer is approximately equivalent to 12.5 years in Florida. This approximates to more than 10 years of exposure in Australia.⁽⁴⁾

Notwithstanding the fact that artificial weathering can not be accurately correlated with natural exposure, it can be seen that 16000 hours provides a large margin for two years exposure in Australia.

Further, Cytec Industries Inc. have shown that the addition of HALS additive UV-3346 at 0.2% provides in excess of 30 months to 50% of original elongation to break, compared with 6-9 months for unstabilised material.

UV Stabilization of 0.25% TiO₂ Pigmented HDPE with CYASORB[®] UV-3346 light stabilizer

<u>Light Stabilizer</u>		<u>Months in Florida to 50% of Original % Elongation*</u>
None		6-9
UV-3346	0.10 %	30
Tinuvin 622**	0.10 %	19
Tinuvin 770**	0.10 %	23
UV-3346	0.20 %	54
Tinuvin 622	0.20 %	30
Tinuvin 770	0.20 %	31

* 60 Mil Micro-tensile bars

** Products of Ciba Specialty Chemicals

- i. In pipe Standards, such as AS/NZS 4130, AS/NZS 4131, and ISO 4437, it is usual to expose pipe specimens, whereas in developmental work on polymers, small specimens are usually chosen, so that the degraded area only is evaluated.

Thus the data presented may be considered conservative, as the bulk material in pipe specimens will lessen the impact of surface degradation.⁽³⁾

For long term use of coloured compounds in service, such as the use of white coextrusions for temperature minimisation, the dosage level of HALS should be increased to maximum compatibility level. For example, Ciba Specialty Chemicals recommend inclusion of 0.4% Tinuvin 783, plus at least 2% of TiO₂ rutile.⁽⁵⁾

In addition to providing the white colour, TiO₂ will impart improved UV resistance, although its effect is not as pronounced as with PVC.

This will optimise performance for the 15 years required by the mining industry.

However, in order to quantify performance, natural and/or artificial weathering tests should be conducted.

ii. **Synergistic effects**

It is known that stabilisers may act in combination with pigments and antioxidants to produce a combined and otherwise unpredictable effect on UV resistance.

For example, testing of HDPE by Chevron Phillips Chemical Company LP⁽³⁾ has shown that for certain yellow pigments, 2% dosage is superior to 1% dosage without stabilisation, but with stabilisation the performance is reversed.

The synergistic effect demands exposure testing, by natural exposure and/or Weather-Ometer. It is recommended that in this context, Weather-Ometer testing be used only for comparative purposes against data established from natural exposure plus Weather-Ometer. In any case, all coloured compounds should eventually be assessed by natural exposure testing.

Exposure Testing:

Where neither carbon black nor HALS is incorporated, compounds to AS/NZS 4130 and AS/NZS 4131 must be subjected to natural exposure testing. Exposure testing is usually carried out at a facility located at Townsville, where incident energy is high, resulting in shorter exposure times.

3.5 GJ/m² equates to about 6 months at Townsville during Spring/Summer whereas 14 GJ/m² equates to about 24 months.⁽⁴⁾

Due to the potential synergistic effects, all coloured pipe compounds should be evaluated by natural exposure testing to a total incident energy level of 14 GJ/m², but the time period involved is likely to inhibit product development, so an interim acknowledgement of conformance could be granted on the basis of compounds that incorporate 0.2% min. of either Tinuvin 783 or Cytec UV-3346.

Means of Assessment:

Following exposure, pipe specimens are tested to assess effect on key properties: resistance to slow crack growth (ESCR), impact strength, resistance to internal pressure, and thermal stability.

Resistance to slow crack growth and impact strength are usually assessed by some form of notched specimen testing. However, as the notching removes the affected layer, these tests are useless.

Fortunately, changes to both resistance to slow crack growth and impact strength can be indirectly assessed by one test, *change in elongation to break*. The general benchmark in industry is an allowable reduction in elongation to break of 50% of original and this is used for some of the data previously cited. AS/NZS 4131 and ISO 4437 require only that the elongation to break after exposure be $\geq 350\%$, rather than specify a change. Additionally, ISO 4437 requires the original elongation to break to be $\geq 350\%$.

Elongation to break of compounds that meet all other requirements of the Standards is typically greater than about 700%, so the requirement of 350% minimum is effectively 50% change.

As previously stated, the data used as the basis is developed from small specimens and thus conservative compared with exposure of pipes.

Resistance to internal pressure is best evaluated by short term 80°C testing, as this simulates long term performance.

Thermal stability is considered to be of little relevance. Although it relates to pipe life and fusion welding, the former is covered by the tensile and pressure testing, and for the latter, welding techniques require removal of the oxidised layer. Furthermore, it has been demonstrated that the OIT method specified in AS/NZS 4130 and ISO4437 is not appropriate for HALS stabilised materials after exposure and determination of carbonyl index should be made.⁽⁶⁾

Conclusions:

- i. Black pipes to AS/NZS 4130 satisfy end-user requirements for both short and long term use.
- ii. Coloured pipes, including coextrusions, to AS/NZS 4130 may be considered suitable for two years storage under exposure within Australia provided appropriate grades of HALS at dosage rate of 0.2% minimum are used.

Suitable grades include Ciba Specialty Chemicals Tinuvin 783 and Cytec Industries UV-3346.

Confirmation by natural exposure testing to a total energy level of 14 GJ/m² should be conducted.

- iii. For longer periods, such as 15 years in WA, optimum performance is best obtained by incorporating HALS stabilisers up to polymer compatibility level, plus at least 2% of rutile titanium dioxide.

Further quantification should be obtained by outdoors exposure testing.

References:

- (1) G. S. Low, Chevron Phillips Chemical Company LP, Singapore. Private communications.
- (2) D. Gueugnaut, G. Lappai, P.Vautherin, D. Rousselot, Gaz De France. 1993 AGA Symposium, San Antonio TX, pp 252-260.
- (3) Chevron Phillips Chemical Company LP. PE TIB-3.
- (4) K. G. Martin, Solar Weathering Indices for Australian Sites. CSIRO, 1977.
- (5) Mrs. Nathalie Gaullier, Ciba Specialty Chemicals, USA. Private communication.
- (6) L. E. Ahlstrand. Oxygen Induction Time - What does it actually tell us about thermal stability? Proc. Plastics Pipes IX, 1995.

For Further information please contact
Plastics Industry Pipe Association of Australia Ltd
Suite 246, 813 Pacific Hwy, Chatswood NSW 2067
or email plasticpipe@pipa.com.au